

MasterFlow[®] 980 (Formerly known as Masterflow 980 M)

High strength, shrinkage compensated cementitious micro concrete

DESCRIPTION OF PRODUCT

MasterFlow 980 is a ready-to-use product in powder form, which requires only the on-site addition of water to produce a shrinkage compensated micro concrete of predictable performance.

The larger size aggregate of **MasterFlow 980** permits precision grouting of thickness more than 80mm between bedplate and foundation and is especially suitable for use in high ambient temperatures.

TYPICAL APPLICATIONS

MasterFlow 980 is formulated for use at any consistency from fluid to damp-pack, and may be used with confidence for bedding, grouting and precision bearing operations such as:

- Gas or steam turbines
- Generators
- Presses
- Crane rails
- Milling machines
- Precast elements
- Anchor bolts

ADVANTAGES

- Shrinkage compensated
- Formulated for deep section grouting
- Proven and predictable performance
- Excellent workability retention even at high ambient temperatures
- High bond strength to steel and concrete
- Early strength development even at fluid consistency
- Good fatigue and impact resistance
- Micro silica content enhances strength and durability
- Impermeable
- Low heat gain

PACKAGING

MasterFlow 980 is supplied in 30kg bags.

APPLICATION PROCEDURE PREPARATION:

The surface onto which the grout is to be applied should be scabbled to remove laitance and expose aggregate. Do not use bush hammers or similar preparation equipment that can crush the aggregate but leave it in place. The surface must be free of oil, dust, dirt, paint, curing compounds, etc. Soak area to be grouted with water for 24 hours prior to grouting to minimise localised absorption and to assist in the free flow of the grout. Surfaces should be damp but free of standing water. Particular attention should be paid to bolt holes to ensure that these are water-free. Use oil-free compressed air to blow out bolt holes and pockets as necessary.

Base plates, bolts, etc. must be clean and free of oil, grease, paint, residual curing compound or other contaminants that could impair adhesion. Set and align equipment. If shims are to be removed after the grout has set, then lightly grease them for easy removal.

Ensure formwork is secure and watertight to prevent movement and leaking during the placing and curing of the grout. The area should be free of excessive vibration. Shut down adjacent machinery until the grout has hardened.

MIXING:

Damp down the inside of the grout mixer with water prior to mixing the initial batch of **MasterFlow 980**. Ensure the mixer is damp but free of standing water. Add 90% of the pre-measured quantity of water. Slowly add the **MasterFlow 980**, mixing continuously. Mix for 2 minutes until a smooth, uniform, lump-free consistency is achieved; then add the remaining water and mix for a further 3 minutes.

MasterFlow[®] 980 (Formerly known as Masterflow 980 M)

PLACING:

Lengths of metal strapping laid in the formwork prior to placing may be necessary to assist grout flow over large areas and in compacting and eliminating air pockets. Pour the grout continuously. Maintain a constant hydrostatic head, of at least 15cm.

On the side where the grout is to be poured, allow 10cm clearance between the side of the form and the base plate of the machine.

On the opposite side, allow at least 10cm clearance between the formwork and the base plate to allow the grout to flow through without entrapping air.

MasterFlow grouts are suitable for use with most types of pumping equipment.

Immediately after placing **MasterFlow 980** grout, cover all exposed grout with clean damp hessian and keep moist until grout is firm enough to accept a curing membrane. We recommend the use of a curing membrane from our **MaterKure** range.

SHOULDERS

Due to differences in temperature between the grout under the base plate, and exposed shoulders that are subject to more rapid temperature changes, de-bonding and/or cracking can occur. Avoid shoulders wherever possible.

If shoulders are required, they should be firmly anchored with reinforcing to the substrate to prevent de-bonding.

TYPICAL WATER REQUIREMENTS:

Application	Consistency	CRD-C-588-79	FLOW CONE CRD-C-79	mix water ltr/30kg	
				min	max
Grouting machinery:	Fluid	-	25-35	3.9	4.2
Grouting machinery:	Flowable	130	-	3.36	3.9
Bedding pre-cast:	Plastic	60	-	2.4	3.0
Filling tie-bar voids:	Dry-pack	-	-	1.8	2.1

FLOWABLE GROUTING TECHNIQUES:

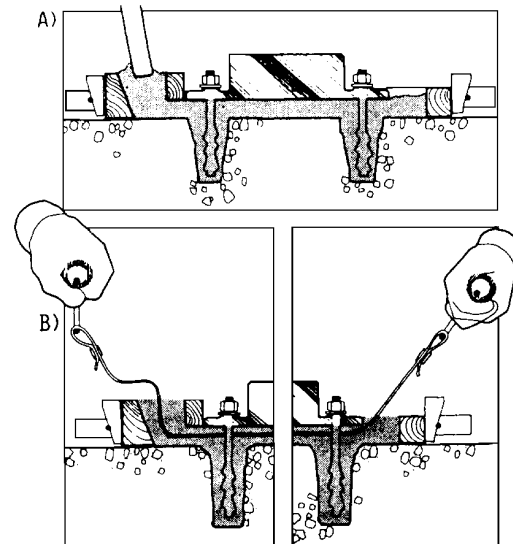


Diagram A illustrates the use of grout surcharge to ensure complete filling under a base.

Diagram B shows that straps can be used to aid grout flow under a wider base. A gentle "sawing" action with the strap allows the grout to flow without segregation for greater distances.

The strength of grout is dependent on many factors, which include mixing, water addition, curing, temperature and humidity. The table below gives typical average strengths of **MasterFlow 980** at 25°C, when mixed with 3.36ltr (flowable) and 4.2tr (fluid) per 30kg bag.

MasterFlow[®] 980 (Formerly known as Masterflow 980 M)

Time	Compressive strengths	
	Flowable N/mm ²	Fluid N/mm ²
1 days	35	28
3 days	50	35
7 days	60	45
28 days	65	58

BLEED WATER:

No bleed water is apparent (ASTM C-232) at recommended water addition rates.

EXPANSION:

Tests were made following both ASTM Standard C-878, on the use of expansive cements and Corps of Engineers Standard for grout. Tests made as prescribed by ASTM Standard C-878 show an expansion value of about 0.05%. Tests in conformity with Corps of Engineers show an expansion value of 0.3%, that is lower than the maximum value (0.4%) fixed by the same standards. Moreover, **MasterFlow 980** expansion occurs both in the plastic and in the early hardened state. However, the expansion action of **MasterFlow 980** exhausts mainly during the first 12 hours of curing.

MODULUS OF ELASTICITY:

The static modulus of elasticity, measured by applying a load corresponding to 1/3 of the strength, is approximately 25,000N/mm² at 7 days and 30,000 N/mm² at 28 days.

FATIGUE RESISTANCE:

Cube samples, produced with **MasterFlow 980** and cured 28 days, underwent fatigue tests of 2,000,000 pulsing stresses ranging between 20 and 50N/mm² at a frequency of 500 cycles/min. Tested specimens were undamaged and their compressive strength was higher than that of similar specimens that were not subjected to fatigue tests.

BOND TO CONCRETE:

After a 28-day curing period, the **MasterFlow 980** concrete bond was determined (about 6.5N/mm²) by the load applied to cause the disbondment from the contact surface.

BOND TO STEEL:

The bond of **MasterFlow 980** to steel, calculated by applying loads to the bars undergoing pull-out tests and by the grout-steel contact surface, is 3N/mm² at 7 days and 4N/mm² at 28 days for plain bars; 20N/mm² at 7 days and 30N/mm² at 28 days for deformed bars.

WORKABILITY:

Tests were made using ASTM C-230 apparatus and compliance with CRD-C-611 was exceeded within recommended water addition rates for plastic and flowable consistencies.

CAPILLARY PORES AND PERMEABILITY:

Even under a pressure of 20 atm, water does not penetrate **MasterFlow 980** specimens. The permeability factor is calculated to be, therefore, lower than 1.10-12 cm/sec.

RESISTANCE TO CHEMICAL ATTACK

Due to its water tightness, **MasterFlow 980** grout is protected against environmental aggressive agents in solution.

RESISTANCE TO HIGH TEMPERATURE:

MasterFlow 980 grouts can withstand high temperature (+400°C) for very long periods without substantial deterioration.

RESISTANCE TO LOW TEMPERATURE:

After 300 freezing and thawing cycles, the modulus of elasticity decreases only 5%. This indicates that **MasterFlow 980** is highly resistant to the disrupting action of frost.

MasterFlow[®] 980 (Formerly known as Masterflow 980 M)

STORAGE

Store out of direct sunlight, clear of the ground, on pallets protected from rainfall. Avoid excessive compaction.

Failure to comply with the recommended storage conditions may result in premature deterioration of the product or packaging. For specific storage advice, consult BASF's Technical Services Department.

SHELF LIFE

Up to 18 months if stored in unopened containers according to manufacturer's instructions.

PRECAUTIONS

The temperature of both the mixed grout and elements coming into contact with the grout should be in the range of +5°C to <35°C. Do not use water in an amount or at a temperature that will produce a consistency more than fluid or cause mixed grout to bleed or segregate.

MasterFlow 980 is formulated for thickness above 80mm, however it is suitable for use at a minimum thickness of 25mm. For applications below 80mm, consider the use of **MasterFlow 928** and for applications below 10mm, consult BASF's Technical Services Department for advice.

To simulate on-site conditions, it is necessary to restrain cubes for the first 24 hours immediately after casting.

DO NOT OVERWORK AND AVOID USING MECHANICAL VIBRATION.

UNDER NO CIRCUMSTANCES SHOULD **MasterFlow 980** BE RETEMPERED BY THE LATER ADDITION OF WATER.

It is essential that a mechanically powered grout mixer is used to obtain the optimum properties.

YIELD/CONSUMPTION

15.12-15.6ltr/30kg bag, dependent on water addition rate 65 x 30kg bags/m³

NOTE

The fatigue and impact resistance of **MasterFlow 980** grout is exceeded only by the metallic reinforced, non-catalysed **MasterFlow 885** grout.

The specially prepared metallic aggregate in this product contributes to impact resistance, a desirable property of grout to be subjected to severe dynamic operating forces and repetitive loading such as found in steel and aluminium rolling mills, crane rails, heavy presses, etc.

When a very rapid set is required in areas subject to chemical spillage or contamination, use epoxy grout **MasterFlow 640**.

For additional information on **MasterFlow 980** grout or other shrinkage compensated grouting materials, contact your BASF representative.

SAFETY PRECAUTIONS

As with all chemical products, care should be taken, during use and storage, to avoid contact with eyes, mouth, skin and foodstuffs (which may also be tainted with vapour until product has fully cured). Treat splashes to eyes and skin immediately. If accidentally ingested, seek immediate medical attention. For further information, refer to material safety data sheet.

NOTE

Field service, where provided, does not constitute supervisory responsibility. For additional information, contact your local BASF representative.

BASF reserves the right to have the true cause of any difficulty determined by accepted test methods.



We create chemistry

MasterFlow[®] 980 (Formerly known as Masterflow 980 M)

QUALITY STATEMENT

All products manufactured by BASF Egypt, or imported from BASF affiliate companies worldwide, are manufactured to procedures certified to conform to the quality, environment, health & safety management systems described in the ISO 9001:2008, ISO 14001:2004 & OHSAS 18001:2007 standards.

* Properties listed are based on laboratory controlled tests.

© = Registered trademark of the BASF-Group in many countries

BASF-CC, Egypt
Business Park A, Building A1,
Cairo Festival City, Ring Road
New Cairo, Egypt
Factory: Sadat City, Piece 118
Zone 4
Tel.: +2 25980800
Tel.: +2 012 393 98 44
Fax: +2 25980801
Tel.: +2048 2658107/8
Fax: +2048 2658106

Whilst any information contained herein is true, accurate and represents our best knowledge and experience, no warranty is given or implied with any recommendations made by us, our representatives or distributors, as the conditions of use and the competence of any labour involved in the application are beyond our control.

website: www.master-builders-solutions.basf.com.eg

As all BASF technical datasheets are updated on a regular basis, it is the user's responsibility to obtain the most recent issue. Most recent issue is available on the website at www.master-builders-solutions.basf.com.eg

BASF_CC-EG/Flow_980_09_10/v1/06_14

